

Replaces:
RN 1558-1:2022-07-20

Delivery Conditions for case-hardening steel

Punched disks and rings of 18CrNiMo7-6 for rotors with peripheral speeds <50 m/s

Contents	Page
1 Scope	2
2 References	2
3 Chemical composition	3
4 Physical characteristics	3
5 Manufacturing	3
6 Testing	4
7 Other requirements.....	4

Changes

2023-04-06:

The following changed in comparison to RN 1558-1:2022-07-20:

- a) transfer to new numbering system
- b) updated references
- c) editorially revised

Responsible division: PK	Editor: M. Förste	Approval: see doc. workflow	Technical reference: C. Eschert	Page: 1 / 4
-----------------------------	----------------------	--------------------------------	------------------------------------	----------------

1 Scope

This standard applies to	Material-No.:	1.6587
	Material designation:	18CrNiMo7-6
	Delivery conditions:	Punched disc, Ring hot formed; unmachined / preturned
	Use case:	rotors with peripheral speeds < 50 m/s

2 References

The following documents, cited in part or in whole, shall apply for the use of this standard. In the case of dated references, only the referenced edition applies; in the case of undated references, the latest edition of the referenced document (including all amendments) applies. The applicable version of the standards listed below shall apply to all contents not covered by this factory standard.

DIN 50125	Testing of metallic materials - Tensile test pieces
DIN 50602:1985-09	Metallographic examination; microscopic examination of special steels using standard diagrams to assess the content of non-metallic inclusions
EN 10021	General technical delivery conditions for steel products
EN 10204	Metallic products - Types of inspection documents
EN 10228-3	Non-destructive testing of steel forgings - Part 3: Ultrasonic testing of ferritic or martensitic steel forgings
EN ISO 148-1	Metallic materials - Charpy pendulum impact test - Part 1: Test method
EN ISO 642	Steel - Hardenability test by end quenching (Jominy test)
EN ISO 643	Steels - Micrographic determination of the apparent grain size
EN ISO 683-3	Heat-treatable steels, alloy steels and free-cutting steels - Part 3: Case-hardening steels
EN ISO 9712	Non-destructive testing - Qualification and certification of NDT personnel
RN 72	Packaging and Preservation; Supply parts for production
RN 1089	Rings; Machining allowances and tolerances
RN 1092	Punched disks; Machining allowances and tolerances
RN 1550	Material samples
RN 1567	Remanent magnetism in components
RN 1936	Labelling; Raw material, parts and gearboxes

3 Chemical composition

Table 1 Chemical composition in %

	C	Si	Mn	P	S	Cr	Mo	Ni	V	Cu
min	0,15		0,50			1,50	0,25	1,40		
max	0,21	0,40	0,90	0,025	0,010	1,80	0,35	1,70		0,30
	Sn	Al	N	Ti	Nb	Sb	O ₂	Ca	H ₂	Al / N
min		0,02	0,008							
max		0,05	0,015	0,006			25 ppm	0,0015	2,0 ppm	4,0

4 Physical characteristics

Table 2 Mechanical properties

(Test temperature: 20 °C)

	Rm	Rp _{0,2}	A5 [%]			Z [%]			Av [J]		
	[N/mm ²]	[N/mm ²]	length.	tang.	cross.	length.	tang.	cross.	length.	tang.	cross.
	min	min	min	min	min	min	min	min	min	min	min
rings	1080	785	--	10	8	--	35	25	--	35	25
punched discs	1080	785	12	10	8	45	35	25	45	35	25

Note: The final mechanical properties can only be achieved after heat treatment (case hardening or quenching and tempering), which is usually carried out at REINTJES. When delivered, the material has lower strengths (see para. 5 c).

a) Structure, inclusions

- grain size, standard: EN ISO 643 standard series: Table C.1; G ≥ 5
- purity degree, standard: DIN 50602 method: K; K4 ≤ 20

b) Hardenability

- standard: EN ISO 683-3 scatter band: +HH
- testing: EN ISO 642
- end distance [mm]: 5 11 25 40
- hardness [HRC]: 42-48 40-47 35-43 33-41

c) Additional properties

- radioactivity: ≤ 0,10 Bq/g

5 Manufacturing

a) Casting method and forging reduction ratio (VG)

- continuous casting: VG ≥ 5,0 ingot casting: VG ≥ 3,0

b) Melting

- making process: E, LD, ESU (on special request)
- post-treatment: vacuum degassing (VD) for E or LD

c) Heat treatment

- treatment condition: ∅ Da < 1000: +FP / +QT ∅ Da ≥ 1000: +QT
- treatment method: liquid quenching and tempering
- anneal to: 600 to 850 N/mm² tensile strength

d) Surface condition

- defect depth: ≤ machining allowance
- unmachined: crack and scale free pretreated (on request): Ra 6,3 (max. Rz 63)
- repair by welding: only after approval by REINTJES

e) Manufacturing tolerances: RN 1089 and RN 1092

6 Testing

a) Ultrasonic testing

- standard: [EN 10228-3](#)
- scanning according to: [table 3, type 3b and 3c, grid scanning](#)
- type of testing: [marginal and core zone testing](#)
- probe specification: [4 MHz \(normal and TR probe\)](#)
- sound attenuation: [≤ 6 dB/m](#)
- examiner qualification: [EN ISO 9712, stage 2](#)
- testing accuracy

	<u>diameter</u>	<u>quality class</u>
○ punched disc, preturned / dipping bath zone 1 (gearing):	0,8 × da up to da	4
zone 2 (power transmission):	di up to 2 × di	4
zone 3 (remaining volume):	2 × di up to 0,8 × da	3
○ hot rolled rings, preturned / dipping bath entire diameter:	di up to da	4
○ punched discs and rings, unmachined entire diameter:	di up to da	3

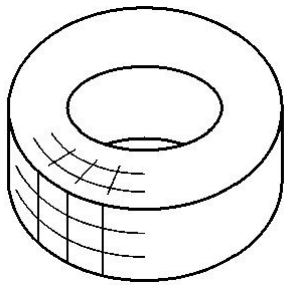


Figure 1 Punched disc / Ring

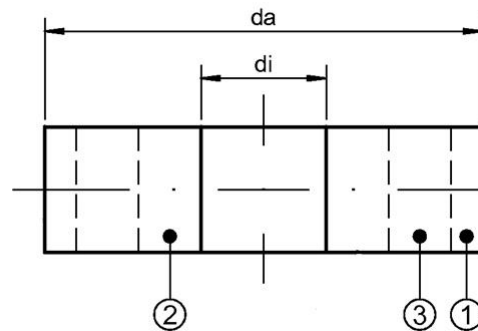


Figure 2 Zones for punched discs / rings

- b) Material identification check: [to be carried out](#)

7 Other requirements

a) steel and forging plant

- certified acc. to: [DIN EN ISO 9001 ff.](#)
- approved by at least two member societies of IACS

b) Packaging and preservation

- [RN 72](#)

c) Sample material and collection

- [RN 1550](#)

d) Remanent magnetism

- [RN 1567](#)

e) Labelling

- [RN 1936](#)

f) Documentation (must be digitally available upon delivery)

- acceptance test certificate EN 10204 - 3.1 per melt and furnace trip or per piece or production lot with specification of primary material and forging ratio
- copy of the acceptance test certificate 3.1 from the steel manufacturer
- evidence of radioactivity and remanent magnetism
- forging schedule (on special request)